

M46J

HIGH MODULUS CARBON FIBER

M46J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan and France.

PRODUCT DESIGNATION

M46J	B	12,000	5	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

* B: Untwisted

FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength 6K	609 ksi	4,200 MPa	TY-030B-01
Tensile Strength 12K	583 ksi	4,020 MPa	TY-030B-01
Tensile Modulus	63.3 Msi	436 GPa	TY-030B-01
Strain at Failure 6K		1.0%	TY-030B-01
Strain at Failure 12K		0.9%	TY-030B-01
Density		1.84 g/cm ³	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	223 g/1000m	TY-030B-03
	12K	445 g/1000m	TY-030B-03

FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.9 α · 10 ⁻⁶ /°C
Specific Heat	0.719 J/g · °C
Thermal Conductivity	0.836 J/cm · s · °C
Electric Resistivity	0.9 x 10 ⁻³ Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

COMPOSITE PROPERTIES*

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	318 Ksi	2,190 MPa	ASTM D-3039
Tensile Modulus*	39 Msi	267 GPa	ASTM D-3039
Tensile Strain		0.83%	ASTM D-3039
Compressive Strength*	158 ksi	1,090 MPa	SACMASRM1R-94
Flexural Strength*	206 ksi	1,420 MPa	ASTM D-790
Flexural Modulus*	32 Msi	222 GPa	ASTM D-790
ILSS	12 ksi	82.8 MPa	SACMASRM1R-94
In Plain Shear Strength	11 ksi	77 MPa	ASTM D-3518
90° Tensile Strength	7 ksi	48 MPa	ASTM D-3039

*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.




PACKAGING

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	1.0	II	76	82	192	126	156	12	12
12K	2.0	II	76	82	192	157	156	12	24

Bobbin Type:

Type II

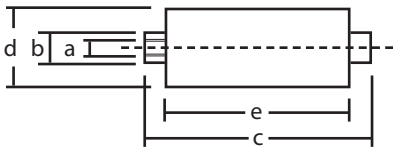

Please refer to SDS for handling and disposal.

For more information or purchasing inquiries:
sales@toraycma.com | www.toraycma.com | 253-846-1777

The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.